

## Hygiene Prevention in Clay Based Ceramic Tiles by Using the Phosphate Extracted from the Mines of Morocco and Its Effect on Technical Properties

*Fatimazahra Boutaleb*

*Nadia Boutaleb*

Hassan 2 University of Casablanca, Laboratory of Biochemistry,  
Environment and Agri-Food, LBEA URAC36, 20650 Morocco

*Bouchaib Bahlaouan*

Higher Institutes of the Nursing Professions and Techniques of Health  
ISPITS Casablanca 22500, Morocco

*Meryem Hadidi*

*Ghita Radi Benjelloun*

*Fatima Azzahra Louanjli*

*Fatima Ezzahra Doublali*

*Said El Antri*

Hassan 2 University of Casablanca, Laboratory of Biochemistry,  
Environment and Agri-Food, LBEA URAC36, 20650 Morocco

Doi: [10.19044/esipreprint.12.2023.p461](https://doi.org/10.19044/esipreprint.12.2023.p461)

Approved: 10 December 2023  
Posted: 12 December 2023

Copyright 2023 Author(s)  
Under Creative Commons CC-BY 4.0  
OPEN ACCESS

### *Cite As:*

Boutaleb F., Boutaleb N., Bahlaouan B., Hadidi M., Benjelloun G.R., Louanjli F.A., Doublali F.E. & El Antri S. (2023) *Hygiene Prevention in Clay Based Ceramic Tiles by Using the Phosphate Extracted from the Mines of Morocco and Its Effect on Technical Properties*. ESI Preprints. <https://doi.org/10.19044/esipreprint.12.2023.p461>

### **Abstract**

This study offers a simple solution to manufacture ceramic tiles with good technical and hygienic properties in accordance with the ISO standards by integrating phosphate products into the formulation. For phosphate products, three grades were studied: HG-high grade, MG-medium grade and LG-low grade. It has shown, for ceramic tiles generated by dry pressing process and which contain these additives, that there is both an effect of the concentration and the nature of additive on technical and hygienic properties. Mechanical property was improved when the incorporate component is richer in P<sub>2</sub>O<sub>5</sub>. Only the use of HG-high grade and MG-medium grade as an

additive at least 15% makes it possible to satisfy the mechanical requirement. The anti-biofilm effect of the natural phosphate (PN) as additives to manufacture ceramic tiles has been proven, it may prevent the bio adhesion and the biofilm formation by a percentage, which can reach up to at 75% for the HG-high grade and MG-medium grade. This solution could interest professionals and all users who care about the state of hygiene of their ceramic materials sensible to the formation of biofilm, like orthopedic implants, swimming pool tile...etc

---

**Keywords:** Mining; Phosphate; Ceramic tiles; Bacterial bioadhesion; Biofilm; Mechanical properties;

## 1. Introduction

Morocco's mining heritage is very rich of phosphates; it has reported that it contains three quarters of the world's reserves, which allows it to rise among the four main universal producers and exporters (Hakkou et al., 2008; Hakkou et al., 2009; El Berkaoui et al., 2021). Moreover, around ten other minerals (zinc, lead, anthracite, iron, copper, barite, antimony, fluorite, cobalt, silver and manganese) are regularly produced, and make it possible to enrich this heritage (Mehahad and Bounar, 2020; Zine et al., 2020). In addition, clays from Morocco occupy a predominant place in all sedimentary rocks. Their mineralogical and physicochemical properties arouse particular interest in many applications including water treatment, paint, barrier for pollutants, adsorbent, catalyst, and the manufacture of construction products (Harti et al., 2007). However, Morocco is known to be a major consumer of clay. The reserves of this materials in Morocco are largely sufficient to ensure totally or partially the supply of the ceramic industry (Harti et al., 2007; El Ouahabi et al., 2014). Ceramics products for interior, exterior and wall coverings, for floors, for bathrooms, public hammams and also for ceramic swimming pools are among the sectors that constitute Morocco's cultural heritage. With development and urbanization, their productions are increasingly in demand and also modernized to meet all the requirements, aesthetic, thermal insulation, energy saving, durability, etc. Unfortunately, their productions in the field of ceramics remains most often artisanal and semi-industrial (dominated by family companies and artisans) and many problems remain and encounter daily by ceramists to bring their products into conformity with local and global technical and regulatory requirements. Despite the abundant literature on this subject (Harti et al., 2007, Sadik et al., 2014), the scarcity of specific studies on the raw material used and the formulation adapted are often responsible for many problems during production, which we can cite breakage, deformations or

malformations of finished products. These problems significantly limit yields. Controlling the quality of ceramic tiles requires very broad knowledge in various scientific fields (geology, mineralogy, geochemistry, formulation, thermodynamics, mechanics, etc.) because of the multitude and diversity of steps in the manufacturing process. In a context of hygiene, given that ceramic coatings have in most cases faced with a humid environment, this makes them conducive to the formation of biofilms (Boutaleb et al., 2008a,b). This work aims to propose a simple solution, which consists in combining the local mineral wealth of Morocco, to produce ceramic tile products with good hygienic and technical properties (mechanical, shrinkage, absorption...). The effect antibiofilm of the natural phosphate (PN) as additives has already been proven in previous research work, in particular on the biomaterials of orthopedic implants based on calcium phosphates and in particular hydroxyapatite (Ferraz et al., 2004; Ramos et al., 2018). This effect will be confirmed also during this research work for ceramic materials by using of various grade of phosphate: HG-high grade, MG-medium grade and LG-low grade incorporated into the base formula used to produce the ceramic tile products.

## 2. Material and method

### 2.1. Materials and characterisation

The phosphates used is from the Cherifien Phosphates Office Group (OCP) – Ouled Abdoun - Beni-Idir (Khouribga in Morocco). Several grades are used: HG-high grade, MG-medium grade and LG-low grade. Their content in BPL and  $P_2O_5$  is shown at Table 1.

**Table 1.** Percentage in BPL and  $P_2O_5$  in different product

	BPL* (%)	$P_2O_5$ (%)
<b>High grade (HG)</b>	> 69.5	31.80
<b>Medium grade (MG)</b>	68<BPL<69.5	31.12< $P_2O_5$ <31.80
<b>Low grade (LG)</b>	61<BPL≤68.0	27.91< $P_2O_5$ <31.12

\*Phosphate concentration is usually expressed as a percentage of  $P_2O_5$  or its  $Ca_3(PO_4)_2$  equivalent, known by the acronyms B.P.L. (Bone Phosphate of Lime):  $P_2O_5 = BPL \times 0.4576$ .

The abundant local clay from the region of El Gara (33°16' 42.7"N 7°13' 39.6" W) was used to prepare the studied mixtures. This region is part of the Triassic basin of Mohammedia– Benslimane-El Gara-Berrechid (Afenzar and Essamoud, 2017). Particle size analysis of clays is carried out according to the method described by the United States Department of

Agriculture United States Department of Agriculture (USDA) (ASTM, 1972). The chemical composition of all geomaterials used was determined by X-ray fluorescence using the WDXRF, S4 Pioneer device supplied by BRUKER S8® (Boutaleb et al., 2020a,b). The chemical structure was studied by infrared spectroscopy using Affinity-1S SHIMADZU spectrometer, in the range between 400–4000  $\text{cm}^{-1}$  at a resolution of 16  $\text{cm}^{-1}$ .

## 2.2. Manufacturing of the ceramic tiles specimens

For the preparation of the tile specimens, the various mixtures were introduced in a dry state and homogenized in a ball mill jar of 500 g capacity. The mixture is added to distilled water (4%) and Fluicer® deflocculates (1%). Mixing of all the ingredients lasts 30 min. The slurry recovered is dried in an industrial roller dryer at a temperature of up to 110 ° C for 30 min. The product obtained is then ground, sieved (particle size <63  $\mu\text{m}$ ) and humidified using a sprayer within limits of 4 to 6% water. Pellets approximately 60 mm in diameter and 7 mm thick were prepared by manual pressing under uniaxial pressure (200 bars) using a hydraulic press of the Sassuolo Lab ® type. A final firing step at 1200 ° C is applied, which lasts 40 min (Boutaleb et al. 2020a,b,c). The tests from F1 to F11 were organized according to Table 2.

**Table 2.** The different formulas studied Technical and anti bioadhesive properties

Formulas	Clay	Additive		
		BT	MT	HT
<b>F1 (Control)</b>	<b>100%</b>	0%	0%	0%
<b>F3</b>	95%	<b>5%</b>	0%	0%
<b>F4</b>	85%	<b>15%</b>	0%	0%
<b>F5</b>	70%	<b>30%</b>	0%	0%
<b>F6</b>	95%	0%	<b>5%</b>	0%
<b>F7</b>	85%	0%	<b>15%</b>	0%
<b>F8</b>	70%	0%	<b>30%</b>	0%
<b>F9</b>	95%	0%	0%	<b>5%</b>
<b>F10</b>	85%	0%	0%	<b>15%</b>
<b>F11</b>	70%	0%	0%	<b>30%</b>

F1, which does not contain a phosphate additive, consist of a test control, and will make it possible to study the effect of the integration of the phosphate products. For each additive, the three percentages 5, 15 and 30% are tested.

## 2.3. Technical quality control of specimens

Mechanical properties of studied specimens were determined using Shimadzu® single-column machine, EZ LX series according to

international standards NM ISO 10545-3 (2017), and NM ISO 10545-4 (2017). The firing shrinkage and the water absorption are determined using method described by Boutaleb *et al.*, (2020a,b,c).

### 2.5. Anti-bioadhesive properties of tiles

Adhesion tests were performed using bacteria indicating of hygiene *Pseudomonas aeruginosa* (ATCC27853) and *Escherichia coli* (ATCC25922). For each bacterium, suspension with an optical density at 405 nm of between 0.7 and 0.8 is prepared according to the protocol described by El Omari *et al.* (2017, 2018). The adhesion test is conducted by immersing the surfaces in the bacterial suspension for 2 hours at 37°C (Boutaleb *et al.*, 2008a,b; El Omari *et al.*, 2017; El Omari *et al.*, 2018). The surfaces are then collected, washed very gently with sterile distilled water held to remove any cells that are not adhered to and that may distort the count. A microscopic observation in Scanning Electron Microscopy (SEM) Philips, Model XL30 was also conducted for the determination of CFU per unit area and to study the anti-bioadhesive properties of tiles (Boutaleb *et al.*, 2008a,b; El Omari *et al.*, 2017, ; El Omari *et al.*, 2018). Matlab Software was used to convert images of Scanning Electron Microscopy SEM to their digital form and then the calculation of the percentage of surface occupation by bacteria.

## 3. Results and Interpretation

### 3.1. Chemical and physical characterization of clays

The abundant clay from the El Gara region of Morocco show a very high percentage of Silica and Aluminum (Table 3), this indicates, the presence of Kaolinite ( $\text{Al}_2\text{Si}_2\text{O}_5(\text{OH})_4$ ) which help to have low fire shrinkage and allows the manufacture of refractory materials (El Yakoubi *et al.*, 2006; Laibi *et al.*, 2017). The Alumina/Silica ratio provides information on the material's moisture permeability, the greater this ratio the greater the permeability (Sadik *et al.*, 2014).

**Table 3.** Chemical compositions by X-ray fluorescence (wt %) and Particle size characterization (%) of used clay

Particle size characterization (%)	
Clay < 2µm	60
Sand 50-2000µm	15
Silt 2-50 µm	25
Chemical Characterization (%)	
SiO <sub>2</sub>	55.700
Al <sub>2</sub> O <sub>3</sub>	17.000

<b>Fe<sub>2</sub>O<sub>3</sub></b>	6.250
<b>CaO</b>	3.950
<b>MgO</b>	2.700
<b>K<sub>2</sub>O</b>	4.550
<b>Na<sub>2</sub>O</b>	0.400
<b>P<sub>2</sub>O<sub>5</sub></b>	0.100
<b>SO<sub>3</sub></b>	0.130
<b>TiO<sub>2</sub></b>	0.800
<b>MnO</b>	0.150
<b>BaO</b>	0.055
<b>Al<sub>2</sub>O<sub>3</sub>/SiO<sub>2</sub></b>	0.305
<b>Fire loss</b>	7.035

The high amount of calcium (CaO) indicates the richness of the clays in calcite (CaCO<sub>3</sub>) that help in acid-base environment stabilizing and help to generate of refractory monolith essential for thermal resistance. The overall composition of the other oxides (Fe<sub>2</sub>O<sub>3</sub>, MgO, K<sub>2</sub>O and SO<sub>3</sub>) reaches a percentage of 9% according to the results of the chemical composition by X fluorescence (table 3) which shows that our clay is not pure (El Yakoubi et al., 2006; Harti et al., 2007; Hakkou et al., 2016; Laibi et al., 2017). SO<sub>3</sub> when present improve plasticity (El Yakoubi et al., 2006; Laibi et al., 2017). The particle size analysis in Table 3 shows that the clay used is among the category of fine clays according to the conventional classification of the USDA (ASTM, 1972). This type of soil is characterized by high plasticity when humid or compactness when is dry.


### 3.2. Spectral analysis

The vibrations at 532 and 470 cm<sup>-1</sup> showed in Fig. 1a is attributable respectively to the deformations of the Si-O-Al bonds where Al is hexacoordinate and Si-O-Si in the kaolinite. The bands at 702 cm<sup>-1</sup> correspond to a vibration of the Si-O-Al bond where Al is tetracoordinate in kaolinite. Table 4 show the wavenumbers and their correspondent functional groups accordiang to Sadik *et al.*, (2012). The results of this analysis are in accordance with the chemical analysis by X-ray fluorescence, indicating the presence of Kaolinite in the analysed material. The FTIR spectra of different grades of natural phosphate (NP) are presented in Fig. 1b.

**Table 4.** Wavenumbers and their correspondent functional groups for used clay (Sadik et al., 2014)

Wavenumber (cm <sup>-1</sup> )	Attribution
Vibration at 908	Deformation of the Al-OH bond in kaolinite

Intense band centered around 1027 and the band at 640	Vibrations of elongations of the Si-O-Si bond in kaolinite in clay minerals
Bands at 3688 and 3619	Vibration of the O-H bond of the hydroxyl groups of kaolinite
Band at 1113	Vibration of the Si-O bond of kaolinite
Band at 1628	Deformation vibrations of the OH <sup>-</sup> and H <sub>2</sub> O groups

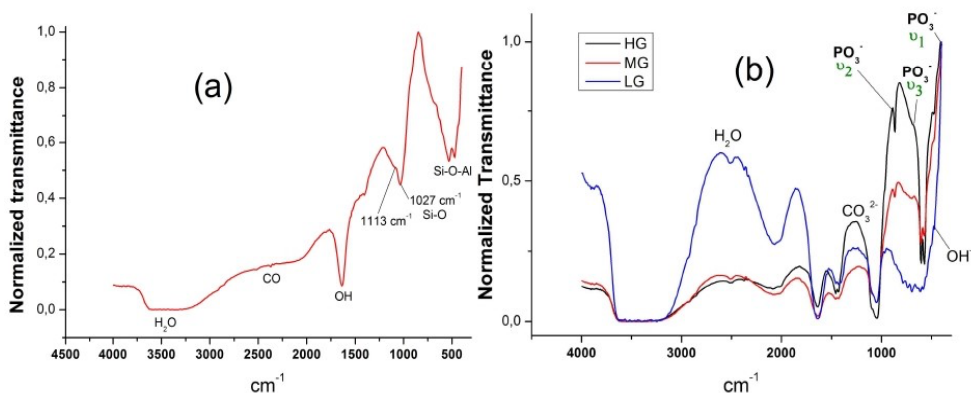


**Figure 1.** Fourier transform infrared spectrum of (a) clay used (b) different grades of natural phosphate (PN)

Different absorption bands were shown, indicating the presence of different functional groups on the NP surface. The intense band at  $1040\text{ cm}^{-1}$  is attributed to the  $\text{PO}_3^{4-}$  group, corresponding to the anti-symmetric valence vibration band domain of the P-O bond. The doublet observed at  $567$  and  $605\text{ cm}^{-1}$ , are attributed to the deformation vibration mode of the P-O bond. The peak at  $1095\text{ cm}^{-1}$  indicates the presence of  $\text{HP}_2\text{O}_4$  groups. Bands at  $870$  and  $1450\text{ cm}^{-1}$  indicate the presence of  $\text{CO}_2^{3-}$  ions. The intense mid band around  $1630\text{ cm}^{-1}$  is attributed to  $\text{H}_2\text{O}$  and  $\text{CO}_2$  groups. The weak peak at  $3540\text{ cm}^{-1}$  indicates the presence of hydroxyl groups of the  $\text{Ca}(\text{OH})$  group. A broad absorption band around  $3700\text{-}3000\text{ cm}^{-1}$  indicates the presence of water molecules and/or hydroxyl groups (Mabroum et al., 2020)


### 3.3. Mechanical and technical properties of the specimens

According to Fig. 2, we note that the gradual addition of the phosphate-rich additive helps reduces weight loss with a more or less stable loss in diameter. This is less visible when the additive is LG-low grade probably because the presence of impurities. The loss of weight often causes the formation of cavities and reduction in density (Weng et al., 2003).

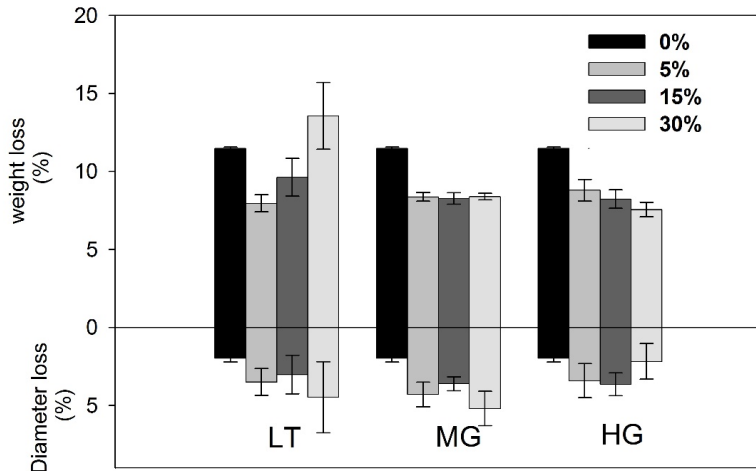

**Figure 2.** Evaluation of the weight and diameter loss in all produced materials.

According to the standards applied in this field (NM ISO 10545-3, 2017; NM ISO 10545-4, 2017), Group III are materials characterized by water absorption percentage that exceeds 10%, and they are not necessarily the first grade. Group II are materials characterized by water absorption percentage between 3% and 10%. Group I are materials characterized by water absorption percentage less than 3%. For all these categories a minimum breaking force of 600 N (for a thickness <7.5 mm) is required (Boutaleb et al., 2020a,c).

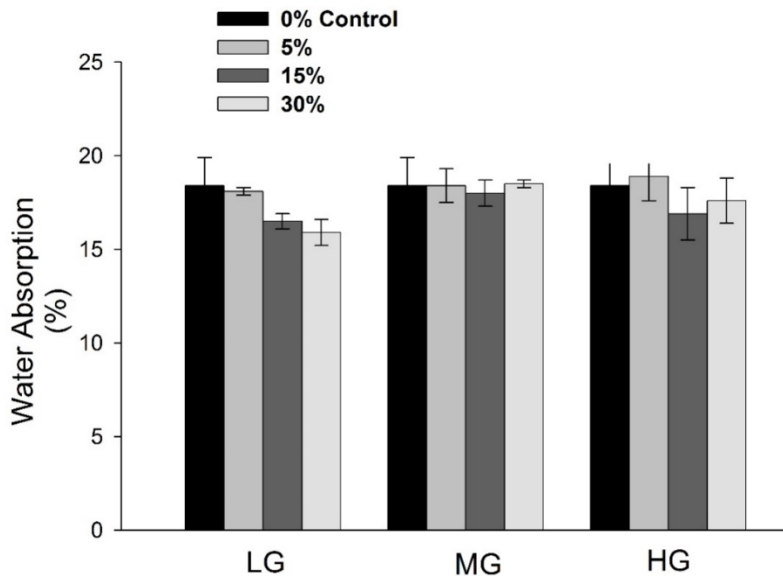

**Figure 3.** Evaluation of the water absorption in all produced materials



Fig. 3 shows that for all materials, the integration on phosphate product additive does not significantly influence the water absorption. When additive is HG-high grade and MG-medium grade the use of at least 15% of each one is necessary to satisfying requirement on the mechanical properties. But, when additive is LG-low grade it is not possible to produce tiles that satisfy the mechanical requirements (Fig. 4).


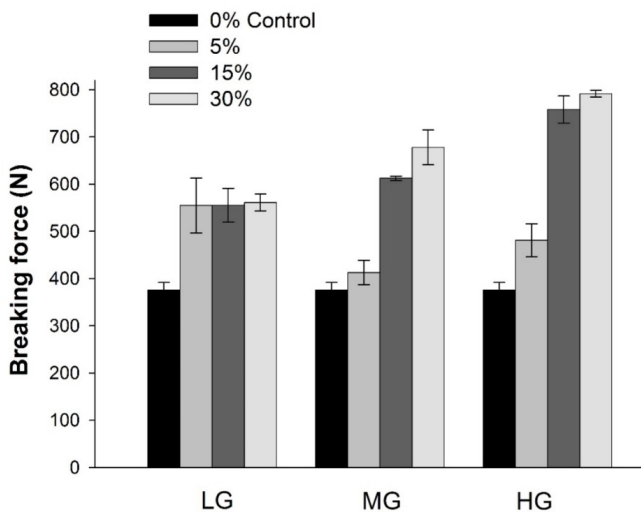


Figure 4. Mechanical properties of the tiles produced.


### 3.4. Anti bioadhesion effect studies

According to the Fig. 5 the adhesion score seems to depend both on the nature of the suspension of bacterial strains, the type of grade used and the percentage integrated into the formulation of each grade. *P. aeruginosa* scores a higher adhesion score than *E. coli* in all the specimens studied. The adhesion score generally respects the following order LG-low grade>MG-medium grade>HG-high grade and decrease when percentage of each additive is greater it is so positively correlated with the  $P_2O_5$  richness. The richer the additive is by this element, the more the percentage of adhesion decreases. *P. aeruginosa* and for *E. coli*, are recorded respectively, a reduction of approximately 61% and 75% for HG-high grade as best results of adhesion inhibition.

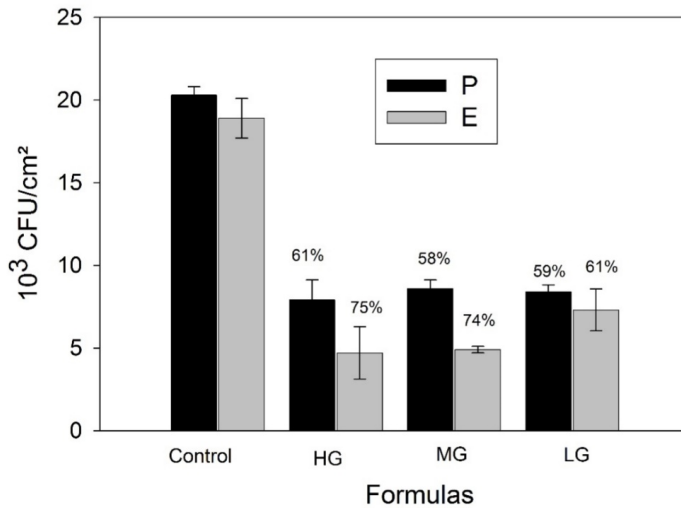

**Figure 5.** Bacterial count results after adhesion test

Fig. 6 show examples of SEM observations. Fig. 6 shows the appearance of the biofilm in the most colonized zones of the surface as a function of bioactive additive richness. It is clearly visible that for low concentrations of bioactive additives we see a more complex and developed structuring of the biofilm, which appears more covered by probably the exopolymer matrix (slime) (El Omari et al., 2017; El Omari et al., 2018).

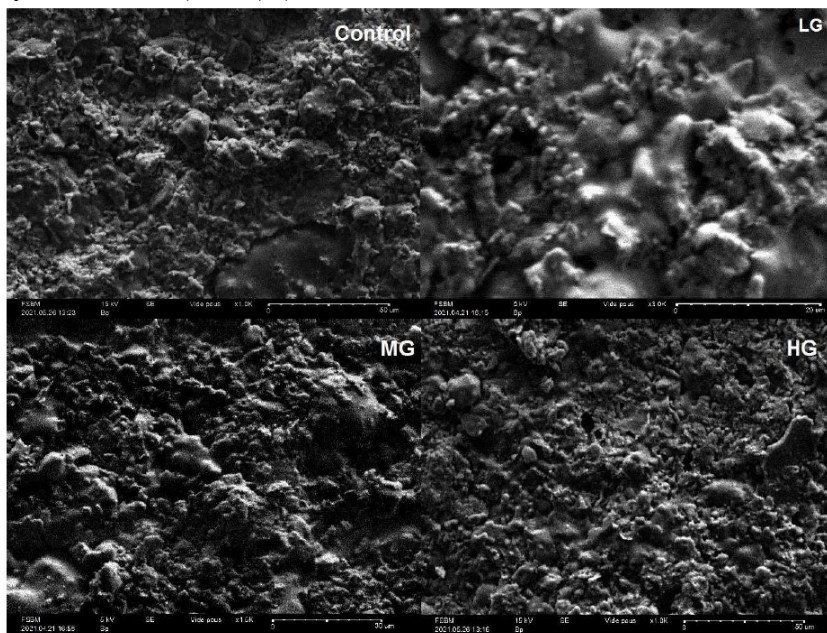

**Figure 6.** MEB observations of the adhesion of *E. coli* on the different surfaces tested

#### 4. Discussion

Improving mechanical and technical quality of ceramic products through the use of specific additives has also been opted for by several authors in the literature. Sawadogo *et al.* (2014) and Amin *et al.* (2019) used talc to improve the technical properties of tiles reducing investment in terms of energy consumption. Yang *et al.* (2017) and Yonghao *et al.* (2017) showed the effect of mining waste rock from phosphate mining activity in China, demonstrating the significant impact on water absorption and technical properties. A similar study by Moukannaa *et al.* (2018), valorizing phosphate sludge produced in large quantities during phosphate ore beneficiation mixed with metakoiline for the production of geopolymers led to reinforced and dense materials with good mechanical properties. The mechanism of the impacts on the recorded shrinkage, absorption and mechanical properties has been mentioned by some authors (Scrivener *et al.*, 2015; Zheng *et al.*, 2015). More specifically the study conducted by Scrivener *et al.* (2015), and Zheng *et al.* (2015), have shown the feasibility of using residues in Portland cement as a filler and explains the impacts on setting time, resistance and drying shrinkage mainly by the dilution effect. Dissolution of phosphorus in the material has a slight retarding effect on hydration, dissolved phosphorus prolongs the induction period, reduces the main heat peak by the precipitation mechanism. In this study, the effect of integration of phosphate products of different grades on technical performance depend so on the concentration and the nature of the grade of phosphate involved in the formulation. More generally, the phosphate content acts, probably, favorably on the mechanical properties of ceramic tiles with almost no effect on water absorption. The weight shrinkage seems to be reduced with the integration of components rich in  $P_2O_5$ . The integration of phosphate products in the formulation improves the mechanical properties of the tiles. Materials that engage either MG or HG at least 15% meet technical requirements. From an anti-adhesion and biofilm-forming standpoint, phosphate products have been studied by several authors for their interesting effects in improving hygiene and treating pollution. Nie *et al.* (2020) propose an efficient and environmentally friendly process for the reduction of  $SO_2$  (desulfurization) using phosphate tailings as an adsorbent. Weng *et al.* (2003), Huang and Nguyen *et al.* (2015); Hakou *et al.* (2016) have shown the efficiency and capacity of residues and different forms of phosphate in my multimetal depollution, adsorption thus in improving hygiene. This study shows that the integration of phosphate products in the formulation improves the hygiene of ceramic tile surfaces and prevents the adhesion and formation of biofilms. Indeed, adhesion tests show a considerable reduction in bacterial growth, which is a function of the  $P_2O_5$  content and can reach 75%. Previous research studies have shown that

the adhesion of bacteria to surfaces depends on the nature of the material (Ferraz et al., 2004; Boutaleb et al., 2008b, El Omari et al., 2017, El Omari et al., 2018). When the material has no bioactive properties, its physico-chemical properties (e.g. hydrophobicity, acid-base character, electrostatic properties) imposed by the presence of molecules and chemical groups exposed to the surface, decide when its affinity or not towards the bacteria, itself capable of modeling their surface properties to resist against environmental stress. But when a material has bioactive properties, it can govern and mask the effect of physico-chemical interactions, also called non-specific (Ferraz et al., 2004; Boutaleb et al., 2008b; El Yakoubi et al. 2006; El Omari et al. 2018).

## Conclusion

This study proposes solutions to improve mechanical and hygienic properties of ceramic tiles product and prevent the adhesion and formation of biofilms by using phosphate products as an additive in the formulation. It was shown that the effect on both mechanical and hygienic properties is proportional to the content of  $P_2O_5$  in the additive. An addition of at least 15% Medium Grade and 15% High Grade is necessary to meet ISO requirements and also gives the ceramic material anti-biofilm properties

## Acknowledgements

Authors would like to thank Espano Cerame Company; Cherifien Phosphates Office Group (OCP) Beni-Idir phosphate production and enrichment unit (Khouribga); Research Center of Materials and Energy of the Hassan II University of Casablanca; CNRST for its technical support.

**Conflict of Interest** All authors declare no conflict of interest

**Ethical approval** This study was conducted in full accordance with ethical principles. All experimental protocols were carried out in accordance with the relevant guidelines and regulations.

**Competing interests** The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

**Funding** The authors would like to thank CNRST for its financial support of PPR2/2016/21 and Research Center of Materials and Energy of the Hassan 2 University of Casablanca

**Data availability statement** The data that support the findings of this study are available from the corresponding author upon reasonable request.

**References:**

1. Afenzar, A., & Essamoud, R. (2017). Early Mesozoic Detrital and Evaporitic Syn-Rift Series of Mohammedia-Benslimane-ElGara-Berrechid Basin (Meseta, Morocco): Sedimentary and Palaeoenvironmental Evolution and Comparison with Neighboring Basins. *International Journal*, 6(1), 596-621. <https://doi.org/10.23953/cloud.ijaese.330>
2. Amin, S. H. K., Elmahgary, M. G., & Abadir, M. F. (2019). Preparation and characterization of dry pressed ceramic tiles incorporating ceramic sludge waste. *Ceram. Silik*, 63, 11-20. <https://doi.org/10.13168/cs.2018.0041>
3. ASTM, American Society for Testing Material, Standard Method for Particle-size analysis of Soil, D. 422-63 (Reapproved 1972) Annual Book of ASTM Standards. Part, 1974, 19, 70-80.
4. Boutaleb, F., Boutaleb, N., Bahlaouan, B., Deblij, S., El Antri, S. (2020a). Effect of Phosphate Mine Tailings from Morocco on the Mechanical Properties of Ceramic Tiles, *International Journal of Engineering Research and Technology (IJERT)* Volume 09, Issue 02 (February 2020). <https://doi.org/10.17577/IJERTV9IS020092>
5. Boutaleb, F., Boutaleb, N., Bahlaouan, B., Deblij, S., El Antri, S. (2020b). Production of ceramic tiles by combining Moroccan phosphate mine tailings with abundant local clays. *Mediterranean Journal of Chemistry*, 10(6), 568-576. <https://doi.org/10.13171/mjc10602006221445nb>
6. Boutaleb, F., Boutaleb, N., Bahlaouan, B., El Antri, S. (2020c). Valorization of phosphate mining waste rock in Morocco in the manufacture of ceramic tiles. *Valorisation du stérile d'exploitation des phosphates au Maroc dans la fabrication de carreaux céramiques (Fr)*. *TSM* 3 - Page(s) 37-43. <https://doi.org/10.36904/tsm/202003037>
7. Boutaleb, N., Latrache, H., & Sire, O. (2008a). Interactions bactéries-matériaux dans les canalisations d'eau potable. *Techniques Sciences Méthodes*, 11, 73-80. <https://doi.org/10.1051/tsm/200811073>
8. Boutaleb, N., Latrache, H., & Sire, O. (2008b). Bioadhésion bactérienne dans les réseaux d'eau potable : effets des matériaux et des facteurs environnementaux. *Techniques Sciences Méthodes*, (5), 37-43. <https://doi.org/10.1051/tsm/200805037>
9. El Berkaoui, M., El Adnani, M., Hakkou, R., Ouhammou, A., Bendaou, N., & Smouni, A. (2021). Phytostabilization of phosphate mine wastes used as a store-and-release cover to control acid mine drainage in a semiarid climate. *Plants*, 10(5), 900. <https://doi.org/10.3390/plants10050900>

10. El Omari, H., Boutaleb, N., Bahlaouan, B., Mekouar, M., Jrifi, A., Aitlefqih, S., Cagnon, B., Lazar, S., El Antri, S., (2018). Canalisations d'eau potable : une nouvelle formulation de tubes PVC anti-biofilm. 407, 96-101. Eau, l'Industrie, les Nuisances. <https://www.scopus.com/record/display.uri?eid=2-s2.0-85041960707&origin=inward&txGid=1c0e0b835112b238011711298013b723>
11. El Omari, H., Boutaleb, N., Bahlaouan, Oualich, S., Jrifi, A., Aitlefqih, S., Lazar, S., El Antri S., (2017). Drinking water pipeline : New PVC formulation anti-biofilm for the Moroccan industry. Journal of Materials and Environmental Science (JMES) Volume 8, Issue 12, Page 4444-4450. ISSN: 2028-2508. <https://doi.org/10.26872/jmes.2017.8.12.469> H.
12. El Ouahabi, M., Daoudi, L., & Fagel, N. (2014). Mineralogical and geotechnical characterization of clays from northern Morocco for their potential use in the ceramic industry. Clay Minerals, 49(1), 35-51. <https://doi.org/10.1180/claymin.2014.049.1.04>
13. El Yakoubi, N., Aberkan, M'hamed, & Ouadia, M. (2006). Use potentialities of Moroccan clays from the Jbel Kharrou area in the ceramic industry. COMPTES RENDUS GEOSCIENCE, 338(10), 693-702. <https://doi.org/10.1016/j.crte.2006.03.017>
14. Ferraz, M. P., Monteiro, F. J., Giao, D., León, B., González, P., Liste, S., Serra, J., Arias, J.L. & Pérez Amor, M. (2004). CaO-P2O5 glass-hydroxyapatite thin films obtained by laser ablation: Characterisation and in vitro bioactivity evaluation. Key Engineering Materials, 254, 347-350. <https://doi.org/10.4028/www.scientific.net/KEM.254-256.347>
15. Hakkou, R., Benzaazoua, M., & Bussière, B. (2008). Acid mine drainage at the abandoned Kettara mine (Morocco): 1. Environmental characterization. Mine Water and the Environment, 27, 145-159. <https://doi.org/10.1007/s10230-008-0036-6>.
16. Hakkou, R., Benzaazoua, M., & Bussiere, B. (2009). Laboratory evaluation of the use of alkaline phosphate wastes for the control of acidic mine drainage. Mine Water and the Environment, 28, 206-218. <https://doi.org/10.1007/s10230-009-0081-9>
17. Hakkou, R., Benzaazoua, M., & Bussière, B. (2016). Valorization of phosphate waste rocks and sludge from the Moroccan phosphate mines: challenges and perspectives. Procedia Engineering, 138, 110-118. <https://doi.org/10.1016/j.proeng.2016.02.068>
18. Harti, S., Cifredo, G., Gatica, J. M., Vidal, H., & Chafik, T. (2007). Physicochemical characterization and adsorptive properties of some Moroccan clay minerals extruded as lab-scale monoliths. Applied



- clay science, 36(4), 287-296. <https://doi.org/10.1016/j.clay.2006.10.004>
19. Huang, L., Li, X., & Nguyen, T. A. (2015). Extremely high phosphate sorption capacity in Cu-Pb-Zn mine tailings. *PLoS One*, 10(8), e0135364. <https://doi.org/10.1371/journal.pone.0135364>
  20. Laibi, A. B., Gomina, M., Sorgho, B., Sagbo, E., Blanchart, P., Boutouil, M., & Sohounhloule, D. K. (2017). Caractérisation physico-chimique et géotechnique de deux sites argileux du Bénin en vue de leur valorisation dans l'éco-construction. *International Journal of Biological and Chemical Sciences*, 11(1), 499-514. <https://doi.org/10.4314/ijbcs.v11i1.40>
  21. Mabroum, S., Aboulayt, A., Taha, Y., Benzaazoua, M., Semlal, N., & Hakkou, R. (2020). Élaboration de géopolymères à base de sous-produits argileux issus des mines de phosphate pour des applications de construction. *Journal de la production plus propre*, 261, 121317. <https://doi.org/10.1016/j.jclepro.2020.121317>
  22. Mehahad, M. S., & Bounar, A. (2020). Phosphate mining, corporate social responsibility and community development in the Gantour Basin, Morocco. *The Extractive Industries and Society*, 7(1), 170-180. <https://doi.org/10.1016/j.exis.2019.11.016>
  23. Moukannaa S., Loutou M., Benzaazoua M., Vitola L., Alami J., Hakkou R., Recycling of phosphate mine tailings for the production of geopolymers, *J. Clean. Prod*, 185, 891–903. (2018)
  24. Nie, Y., Dai, J., Hou, Y., Zhu, Y., Wang, C., He, D. et Mei, Y. (2020). Un processus efficace et respectueux de l'environnement pour la réduction du SO<sub>2</sub> en utilisant les résidus miniers de phosphate comme adsorbant. *Journal des matières dangereuses*, 388, 121748. <https://doi.org/10.1016/j.jhazmat.2019.121748>
  25. NM ISO 10545-3., Carreaux et dalles céramique - Partie 3 : Détermination de l'absorption de l'eau, de la porosité ouverte, de la densité relative et la densité apparente (2017)
  26. NM ISO 10545-4., Carreaux et dalles céramique - Partie 4 : Détermination de la résistance à la flexion et module de rupture (2017)
  27. Ramos, J. V. H., Anselme, K., Simon-Masseron, A., & Ploux, L. (2018). Bio-sourced phosphoprotein-based synthesis of silver-doped macroporous zinc phosphates and their antibacterial properties. *RSC advances*, 8(44), 25112-25122. <https://doi.org/10.1039/C8RA04438D>.
  28. Sadik, C., El Amrani, I., & Albizane, A. (2012). Influence de la nature chimique et minéralogique des argiles et du processus de fabrication sur la qualité des carreaux céramiques. In *MATEC Web*

- of Conferences (Vol. 2, p. 01016). EDP Sciences. <https://doi.org/10.1051/mateconf/20120201016>
29. Sawadogo, M., Zerbo, L., Seynou, M., Sorgho, B., & Ouedraogo, R. (2014). Technological properties of raw clay based ceramic tiles: Influence of talc/properties technologiques de careaux céramiques à base d'argiles : Influence d'un talc naturel. *Scientific Study & Research. Chemistry & Chemical Engineering, Biotechnology, Food Industry*, 15(3), 231. <https://pubs.ub.ro/dwnl.php?id=CSCC6201403V03S01A0004>
  30. Scrivener, K. L., Juilland, P., & Monteiro, P. J. (2015). Advances in understanding hydration of Portland cement. *Cement and Concrete Research*, 78, 38-56. <https://doi.org/10.1016/j.cemconres.2015.05.025>
  31. Weng, C. H., Lin, D. F., & Chiang, P. C. (2003). Utilization of sludge as brick materials. *Advances in environmental research*, 7(3), 679-685. [https://doi.org/10.1016/s1093-0191\(02\)00037-0](https://doi.org/10.1016/s1093-0191(02)00037-0)
  32. Yang, Y., Wei, Z., Chen, Y. L., Li, Y., & Li, X. (2017). Utilizing phosphate mine tailings to produce ceramisite. *Construction and building materials*, 155, 1081-1090. <https://doi.org/10.1016/j.conbuildmat.2017.08.070>
  33. Yonghao Y., Wei Z., Chen Y., Li Y., Li X. (2017). Utilizing phosphate mine tailings to produce ceramisite. *Construction and Building Materials*;155:1081-1090.
  34. Zheng, K., Zhou, J., & Gbozee, M. (2015). Influences of phosphate tailings on hydration and properties of Portland cement. *Construction and Building Materials*, 98, 593-601. <https://doi.org/10.1016/j.conbuildmat.2015.08.115>
  35. Zine, H., Elgadi, S., Hakkou, R., Papazoglou, E. G., Midhat, L., & Ouhammou, A. (2020). Wild plants for the phytostabilization of phosphate mine waste in semi-arid environments: a field experiment. *Minerals*, 11(1), 42. <https://doi.org/10.3390/min11010042>